

## Coexistence of Atomic and Molecular Chemisorption States: $H_2/Pd(210)$

Pia K. Schmidt and Klaus Christmann

*Institut für Chemie der Freien Universität Berlin, D-14195 Berlin-Dahlem, Germany*

Georg Kresse and Jürgen Hafner

*Institut für Materialphysik, Universität Wien, A-1090 Wien, Austria*

Markus Lischka and Axel Groß

*Physik-Department T30, Technische Universität München, D-85747 Garching, Germany*

(Received 20 February 2001; published 10 August 2001)

A novel  $H_2$  molecular adsorption state on metal surfaces has been detected by temperature-programmed desorption and electron energy loss spectroscopy experiments of the  $H_2/Pd(210)$  system. The molecular nature of this state has been verified by isotope exchange experiments. This molecular state leads to a decrease of the surface work function while atomic hydrogen on Pd(210) causes an increase. *Ab initio* total-energy calculations have confirmed all experimental findings. Through these calculations the microscopic nature of this novel molecular adsorption state could be identified; it turns out that this state is stabilized by the presence of atomic hydrogen on the Pd(210) surface.

DOI: 10.1103/PhysRevLett.87.096103

PACS numbers: 68.35.Ja, 82.20.Kh, 82.65.+r

The interaction of hydrogen with metal surfaces has served as a benchmark system in surface science. Because of its relative simplicity, numerous experimental and theoretical studies exist that address the energetics and dynamics of hydrogen adsorption and dissociation on metals [1–3]. These studies contributed significantly to our current understanding of the fundamental principles underlying the bond-making and -breaking processes at surfaces. The general picture of hydrogen bonding at surfaces can be summarized as follows [1]: In general, hydrogen adsorbs dissociatively at metal surfaces. While at noble metals the dissociation is hindered by a sizable energy barrier, it occurs spontaneously at most transition metal surfaces. If molecular adsorption states exist, they are usually very weakly bound in shallow physisorption wells requiring surface temperatures below 20 K to stabilize these states [4]. At Ni(510), molecular chemisorption at surface temperatures up to 125 K has been observed, presumably at the steps, but only after the surface was passivated with a dense atomic hydrogen layer [5].

The H/Pd system is of great technological relevance due to its use as hydrogen storage. Among other reasons, this has motivated detailed studies of the hydrogen adsorption structures and energetics [6,7], adsorption and desorption dynamics [8–12], and poisoning phenomena [8,10,13]. In this Letter we report a, so far unknown, phenomenon in the hydrogen-surface interaction, namely, the coexistence of chemisorbed molecular and atomic hydrogen on the relatively open Pd(210) surface *although the surface is not fully passivated*. By a combination of experiment and *ab initio* total-energy calculations within density functional theory (DFT) the molecular adsorption state has been clearly identified. These findings are relevant and important for the general understanding of re-

actions at structured or defect-rich surfaces such as in heterogeneous catalysis.

In order to investigate the hydrogen adsorption on Pd(210), temperature-programmed desorption (TPD), work function change ( $\Delta\Phi$ ), and high-resolution electron energy loss spectroscopy (HREELS) experiments have been performed at surface temperatures  $T$  between 50 and 500 K in an ultrahigh vacuum (UHV) chamber with a base pressure of less than  $3 \times 10^{-11}$  mbar. The UHV chamber was equipped with a liquid He cryostat, a Kelvin probe for the  $\Delta\Phi$  measurements, and an electron spectrometer of the Unwin type [14].

The (210) surface is a relatively open surface that, however, does not exhibit a pronounced terrace structure. The geometry of this surface is shown in Fig. 1. It is known from previous work [15] that hydrogen adsorbs atomically on Pd(210) for  $T > 120$  K in three different binding states  $\beta_1$ ,  $\beta_2$ , and  $\beta_3$  with desorption temperatures of  $\sim 180$ ,  $\sim 250$ , and  $\sim 330$  K, respectively. In addition, at very high

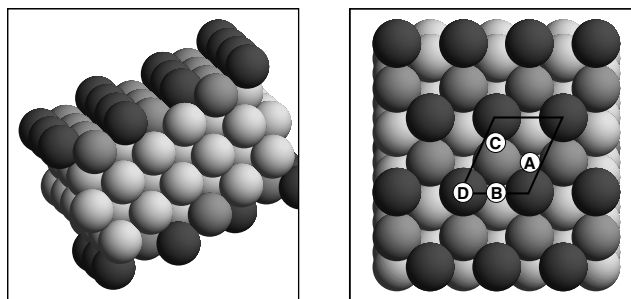


FIG. 1. Side and top view of the (210) surface. In the right panel the surface unit cell plus the three atomic adsorption sites A, B, and C are included. The site D corresponds to the molecular adsorption site.

hydrogen exposures an atomic  $\alpha$  state becomes populated which desorbs at 150 K and is attributed to subsurface hydrogen [15]. The *novel molecular*  $H_2$  species to be described here appears in TPD spectra if the hydrogen is adsorbed at temperatures below 100 K. One typical example is given in Fig. 2a, where TPD spectra for different exposures between 0.02 and 0.2 L at an adsorption temperature of 50 K are plotted. The spectra show, in addition to the atomic  $\beta$  states, one intense state at 94 K with a low temperature satellite at 60 K. These states are denoted as  $\gamma_2$  and  $\gamma_1$ , respectively.

Both states are rapidly and simultaneously filled. Saturation is attained between 0.5 and 1.0 L exposures. The spectra reveal a first order desorption kinetics and desorption energies of 155 meV ( $\gamma_1$ ) and 250 meV ( $\gamma_2$ ). In order to verify the molecular nature of the  $\gamma$  states, we have performed  $H_2/D_2$  isotope exchange experiments. The Pd crystal was first exposed to  $\sim 0.25$  L  $H_2$  and then to the same amount of deuterium,  $D_2$ . We then recorded the 3 amu (= HD) TPD spectrum. An HD signal in the temperature range of the  $\gamma$  states would indicate dissociative adsorption. But in fact, HD is almost entirely absent in this temperature range, as Fig. 2b demonstrates. However, all spectra exhibit HD signals in the temperature range of the atomic states. This indicates that not all of the atomic adsorption sites were filled by H, so that some fraction of the  $D_2$  can dissociate either directly or upon heating during the TPD run. In another series of experiments we first exposed the crystal at temperatures above 125 K with 0.5 L of the one isotope, thus saturating the atomic states, and then at 50 K with the other isotope. The results showed no isotopic scrambling in the  $\gamma$  states and almost no isotope exchange in the  $\beta$  states.

Further details about the  $H_2/Pd(210)$  interaction are revealed by the measurement of the  $H_2$ -induced work function change  $\Delta\Phi$ . Figure 3 shows the work function change as a function of exposure at a temperature of 50 K. After

an exposure of  $\sim 0.1$  L,  $\Delta\Phi$  drops sharply to  $-370$  meV, passes a shallow minimum after 0.3 L exposure, and stabilizes at  $-375$  meV after exposures of 1 L. When the hydrogen-saturated sample, after an exposure of 2 L, is linearly heated to 500 K with a heating rate of 1 K/s,  $\Delta\Phi$  rises steeply to approximately 130 meV, the increase being completed at  $\sim 120$  K. On top of the  $\Delta\Phi$  curve, the simultaneously recorded TPD spectrum is plotted. This spectrum demonstrates that the steep rise of  $\Delta\Phi$  is associated with the desorption of the molecular  $H_2$  adsorption state. For  $T > 120$  K,  $\Delta\Phi$  decreases again, with a particularly marked drop between 300 and 375 K, due to desorption of the atomic  $\beta_3$  species. We also monitored the work function change in the  $H_2/D_2$  isotope exchange experiments. Preadsorption of the one species at  $T > 120$  K, i.e., population of only the atomic adsorption states, leads to a  $\Delta\Phi$  increase of  $\sim 120$  meV, and postadsorption of the other species at 50 K, i.e., population of the molecular adsorption state, causes a strong subsequent drop of  $\Delta\Phi$ .

The molecular nature of the  $\gamma$  states is further confirmed by HREELS results. Our data (not shown here) were taken at 50 K after admission of 0.5 L of  $H_2$  and  $D_2$ . The  $H_2$  spectrum shows a sharp band around 58 meV and a shoulder between 100 and 200 meV which are attributed to atomic H species [15]. In addition, we find a broad loss at about 420 meV which reflects the excitation of the H-H stretching vibration. For  $D_2$ , the respective D-D vibration appears at about 300 meV, as expected from the mass ratio between H and D.

The adsorption of hydrogen on Pd(210) does not lead to any superstructure in low-energy electron diffraction experiments [15]. Hence it is experimentally very difficult to identify the exact location and nature of the hydrogen adsorption states. In order to obtain this microscopic information, we performed DFT calculations with the generalized gradient approximation [16] using the Vienna *ab initio* simulation package [17]. The surface is modeled by an

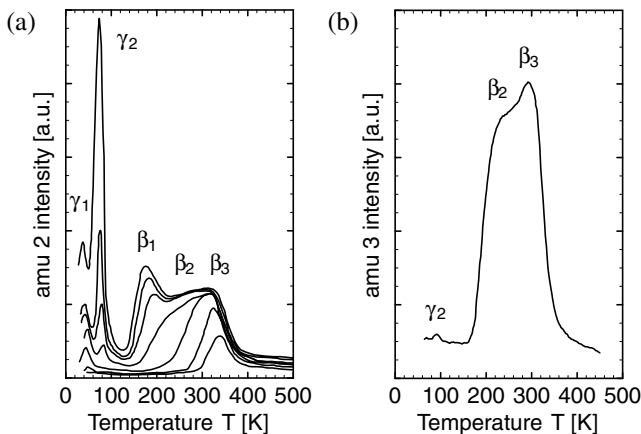


FIG. 2. Thermal desorption spectra. (a) Series of  $H_2$  TPD spectra for different exposures between 0.02 and 0.2 L at a temperature of 50 K. (b) Mass 3 (HD) TPD spectrum after a mixed  $H_2/D_2$  exposure at 50 K.

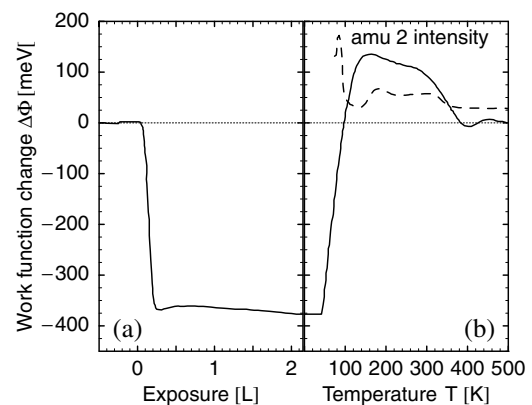


FIG. 3. Hydrogen-induced work function change  $\Delta\Phi$ . (a) Dependence of  $\Delta\Phi$  on  $H_2$  exposure for adsorption at 50 K. (b) Dependence of  $\Delta\Phi$  on the surface temperature after saturation of the Pd(210) with molecular hydrogen. The  $H_2$  TPD spectrum (dashed line, arbitrary units) is also plotted.

eleven-layer slab separated by 11 Å of vacuum. Because of the use of ultrasoft pseudopotentials [18], a cutoff energy of 200 eV was sufficient to obtain converged total energies which were determined by a surface Brillouin zone integration using an  $11 \times 11$   $\mathbf{k}$ -point mesh. The slab, together with the surface unit cell is depicted in Fig. 1. The atomic adsorption sites are denoted by  $A$ ,  $B$ , and  $C$ . A comparison between experimental and theoretical adsorption energies is given in Table I, where the site assignment was done according to the DFT results. The agreement between theory and experiment is indeed very satisfying.

We then determined hydrogen dissociation paths for  $\text{H}_2/\text{Pd}(210)$  in detail. For hydrogen dissociation on the clean  $\text{Pd}(210)$  surface our main result is that at larger distances from the surface the  $\text{H}_2$  molecule is first attracted to the top-layer Pd atom, but at closer distances it spontaneously dissociates into the  $A$  and  $B$  sites (see Fig. 1). Corresponding reaction paths have also been identified for other  $\text{H}_2/\text{Pd}$  systems [7,19]. This means that at the clean  $\text{Pd}(210)$  surface no stable molecular adsorption state exists.

A reexamination of the TPD spectra in Fig. 2a reveals that indeed for very small exposures ( $<0.03$  L) only atomic  $\beta$  states become populated. We have therefore determined hydrogen dissociation paths on hydrogen-precovered  $\text{Pd}(210)$ . It turns out that the hydrogen dissociation in the  $A$  and  $C$  sites is hindered by a barrier of about 220 meV if all  $B$  sites are populated with H atoms. However, the attraction of the  $\text{H}_2$  molecule to the top-layer Pd atom (site  $D$  in Fig. 1b) is hardly influenced by the presence of the preadsorbed H atoms. Thus a metastable molecular adsorption state with a well depth of 270 meV is formed. This state is illustrated in Fig. 4 in a so-called elbow plot of the potential energy surface as a function of the  $\text{H}_2$  center-of-mass distance  $z$  and the H-H distance  $d$  for molecules approaching the top of the top-layer Pd atoms adjacent to the  $B$  sites.

Even for atomic hydrogen coverages of  $\theta = 2$  and 3,  $\text{H}_2$  molecular adsorption wells on top of the first-layer Pd atom are still present, with adsorption energies of 220 and 90 meV, respectively. We associate the molecular wells for  $\theta = 1$  and 2 with the  $\gamma$  peaks in the TPD spectra. This means that the two  $\gamma$  peaks do not correspond to two differ-

ent molecular adsorption sites or states, but just to two different underlying atomic hydrogen coverages (see Table I). In Fig. 2 no molecular adsorption state corresponding to  $\theta = 3$  can be resolved since the adsorption temperature is too high. However, for longer exposures at 30 K an additional molecular state ( $\delta$ ) can be identified between 30 and 40 K as a shoulder in the TPD spectrum which we attribute to this particular state.

Our calculations also confirm the experimental trend in the work function change upon hydrogen adsorption. While atomically adsorbed hydrogen increases the work function by up to 250 meV according to the DFT results, additional molecular hydrogen leads to a work function decrease of more than 700 meV which is somewhat larger than in the experiment. Furthermore, the DFT calculation yields an H-H stretch frequency in the  $\gamma_1$  state of  $\hbar\omega_{\text{vib}} = 422$  meV, which is rather close to the HREELS results of 420 meV.

The good agreement between experiment and theory confirms that we have identified the correct molecular adsorption state. In Fig. 4b an electron density difference plot of this state is shown. It corresponds to the density difference between the interacting system and the isolated  $\text{H}_2$  molecule and the H-covered  $\text{Pd}(210)$  surface. The plot demonstrates the strong hybridization between the  $\text{H}_2$  molecule and the  $\text{Pd}(210)$  surface which is mainly due to the interaction of the Pd  $d_{z^2}$  with the  $\text{H}_2$   $\sigma$  orbital and the interaction of the Pd  $d_{xz}$  and  $d_{yz}$  with the  $\text{H}_2$   $\sigma^*$  orbital [19]. The  $\text{H}_2$  molecule becomes strongly polarized, thus decreasing the work function. On the other hand, the molecular bond is weakened only slightly. The preadsorbed H atoms at the bridge site are located at the same height as the top-layer Pd atoms. Their presence does not significantly disturb the  $\text{H}_2$  interaction with the top-layer atoms at  $\text{H}_2$  distances of more than 1.6 Å. However, these preadsorbed H atoms do hinder the dissociation of further  $\text{H}_2$  molecules at the surface. They thus stabilize the molecular adsorption state.

The following scenario for the hydrogen adsorption on  $\text{Pd}(210)$  can be derived from the combination of experimental and theoretical results. On clean  $\text{Pd}(210)$ , hydrogen adsorbs dissociatively. Once atomic hydrogen is present on the  $\text{Pd}(210)$  surface, further hydrogen dissociation

TABLE I. Atomic and molecular adsorption energies as a function of hydrogen coverage on  $\text{Pd}(210)$ . The atomic adsorption energies are defined as the energies for additional adsorption of one H atom per surface unit cell with respect to the  $\text{H}_2$  molecule in the gas phase. The experimental results have been derived from TPD spectra. The theoretical results were obtained by fully relaxing the adsorbates and the first five Pd layers to their minimum energy configuration. The molecular energies  $E_{\text{ad}}(\text{H}_2)$  correspond to the molecular adsorption on site  $D$  at a surface precovered with atomic hydrogen with the atomic hydrogen coverage per unit cell specified by  $\theta$ . The notation of the sites refers to Fig. 1.

Coverage	$E_{\text{ad}}(\text{H})$ [eV]				$E_{\text{ad}}(\text{H}_2)$ [eV]			
	State	Site	Exp.	Theory	State	Site	Exp.	Theory
$\theta = 1$	$\beta_3$	$B$	0.41	0.42	$\gamma_2$	$D$	0.25	0.27
$\theta = 2$	$\beta_2$	$B, A$	0.33	0.30	$\gamma_1$	$D$	0.16	0.22
$\theta = 3$	$\beta_1$	$B, A, C$	0.23	0.16	$\delta$	$D$	–	0.09

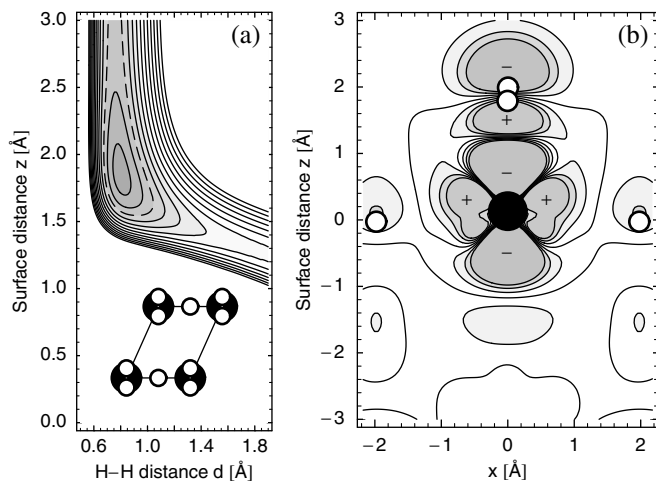


FIG. 4. DFT results of the  $\text{H}_2$  molecular adsorption on the hydrogen-covered Pd(210) surface. (a) Contour plot of potential energy surface. The coordinates in the figure are the  $\text{H}_2$  center-of-mass distance from the surface  $z$  and the H-H interatomic distance  $d$ . The lateral H coordinates are indicated in the inset. The contour spacing is 0.1 eV, and the vacuum energy level is marked by the dashed contour line. (b) Electron density difference plot of the molecular adsorption state in the  $x$ - $z$  plane. The positions of the H atoms and the top Pd atom are marked by open and filled circles, respectively.

becomes kinetically hindered close to the adsorbed hydrogen atoms *although atomic adsorption sites are still available*. This can be regarded as a local self-poisoning of hydrogen dissociation. In Fig. 3 almost no initial increase of the work function upon atomic hydrogen adsorption can be detected due to the low coverage that does not produce any significant work function change, but we always find a pronounced initial increase in the work function, in particular for smaller hydrogen fluxes. At higher coverages the work function change is then dominated by the strong decrease caused by the adsorbed  $\text{H}_2$  molecules. A similar scenario might also be valid for the adsorption of hydrogen on stepped Ni surfaces, such as the one studied in Ref. [5] which we are planning to check by studying the system  $\text{H}_2/\text{Ni}(210)$ .

Interestingly enough, Fig. 2a shows that the weaker bound  $\gamma_1$  state becomes populated first. This corresponds to  $\text{H}_2$  adsorption on a Pd(210) surface with two hydrogen atoms per surface unit cell. One might speculate that apparently the first dissociated H atoms stay within one unit cell, i.e., the single H atoms are not very mobile after dissociation and end up in the nearest available adsorption sites that do not correspond to the most stable ones. This means that at an adsorption temperature of 50 K the population of the atomic adsorption states is not in thermal equilibrium. This view is supported by the fact that at an adsorption temperature of 100 K, which apparently allows one to be closer to thermal equilibrium, the weakly bound

$\beta_1$  state appears only at an exposure of 1.0 L [15], i.e., for the exposures corresponding to the spectra of Fig. 2a it is not populated. Further evidence comes from the findings that the ratio of the  $\gamma_1$  to the  $\gamma_2$  peak depends sensitively on the specific adsorption conditions of the experiment. On the other hand, the largest exposure shown in Fig. 2a, 0.2 L, does not correspond to the saturation of all the atomic states so that  $\gamma_2$  states can still be populated.

In conclusion, by a combination of experiment and theory we have identified a *novel molecular* chemisorption state of  $\text{H}_2$  on Pd(210) with a binding energy of  $\sim 250$  meV. This state is stabilized by the presence of atomic hydrogen at the surface. The preadsorbed atomic hydrogen does not significantly disturb the interaction of the  $\text{H}_2$  molecules with the Pd atoms as long as the  $\text{H}_2$  molecules are farther away from the surface, but it hinders the  $\text{H}_2$  dissociation on Pd(210) although atomic adsorption sites are still available.

Financial support of this work by the Deutsche Forschungsgemeinschaft, through Project No. CH64-1, and Sonderforschungsbereich 338 is gratefully acknowledged.

- 
- [1] K. Christmann, Surf. Sci. Rep. **9**, 1 (1988).
  - [2] A. Groß, Surf. Sci. Rep. **32**, 291 (1998).
  - [3] G. J. Kroes, Prog. Surf. Sci. **60**, 1 (1999).
  - [4] S. Andersson and J. Harris, Phys. Rev. B **27**, 9 (1983).
  - [5] A.-S. Mårtensson, C. Nyberg, and S. Andersson, Phys. Rev. Lett. **57**, 2045 (1986).
  - [6] R. J. Behm, K. Christmann, and G. Ertl, Surf. Sci. **99**, 320 (1980).
  - [7] S. Wilke and M. Scheffler, Phys. Rev. B **53**, 4926 (1996); A. Eichler, G. Kresse, and J. Hafner, Surf. Sci. **397**, 116 (1998).
  - [8] K. D. Rendulic, G. Anger, and A. Winkler, Surf. Sci. **208**, 404 (1989).
  - [9] A. Groß, S. Wilke, and M. Scheffler, Phys. Rev. Lett. **75**, 2718 (1995); A. Groß and M. Scheffler, Phys. Rev. B **57**, 2493 (1998).
  - [10] G. Comsa, R. David, and B.-J. Schumacher, Surf. Sci. **95**, L210 (1980).
  - [11] L. Schröter, H. Zacharias, and R. David, Phys. Rev. Lett. **62**, 571 (1989).
  - [12] D. Wetzig *et al.*, Phys. Rev. Lett. **76**, 463 (1996).
  - [13] S. Wilke and M. Scheffler, Surf. Sci. **329**, L605 (1995); A. Groß, C.M. Wei, and M. Scheffler *ibid.* **416**, L1095 (1998).
  - [14] R. Unwin *et al.*, Rev. Sci. Instrum. **55**, 1809 (1984).
  - [15] U. Muschiol, P.K. Schmidt, and K. Christmann, Surf. Sci. **395**, 182 (1998).
  - [16] J.P. Perdew *et al.*, Phys. Rev. B **46**, 6671 (1992).
  - [17] G. Kresse and J. Furthmüller, Phys. Rev. B **54**, 11 169 (1996); Comput. Mater. Sci. **6**, 15 (1996).
  - [18] D. Vanderbilt, Phys. Rev. B **41**, 7892 (1990).
  - [19] G. Kresse, Phys. Rev. B **62**, 8295 (2000).